

DIPLOMA PROJECT THESIS

02 June 2025

Hempcrete Construction  
A Strategic Guide to Method Selection & Mainstream  
Adoption

By

Theodore Gush

529378

With the support and mentoring of;

Jan Jakub Tesar Ph.D.

&

Ales Marek Ph.D.

CVUT

Faculty of Architecture 15127



**FAKULTA  
ARCHITEKTURY  
ČVUT V PRAZE**

# Executive Summary

## The Focus

This thesis is deliberately focussed on the use of hempcrete (and other compatible Bio-based materials) currently in use in the construction sector. It does not seek to replicate the growing body of existing publications on this subject but rather to drill down into the practical implications for architects and specifiers of contemplating its use in their future projects. In approaching the agreed Project Assignment for the Thesis, I soon realised that my observations and analysis would suggest that the Expected Solutions would fall into two compatible yet slightly different sections.

## The Main Output

The first section focuses on the 'Main Output' and is inevitably informed by my own lived experience of designing and building with hempcrete for about ten years. I shall be explaining to the readers the full scope of the different ways of using the materials to suit the different circumstances of particular site constraints, structural needs and sequencing challenges.

## Constraints and Design Decisions

The thesis makes many references to the 'Decision Matrix'. I believe this a first on this specific topic as I have come to realise that a different approach to design development is key to understanding the optimum way of determining build strategies and sequencing when using these highly effective materials. In this method of wall construction specifiers are advised to review multiple elements of the wall build that will inform their best option for the design scheme prior to determining their chosen project design. These elements involve not only the choice of materials but also; several different types of structural framing, site access (to both the inside and outside of the wall), application of the hempcrete (dry blocks and panels, wet sprayed on or cast in-situ and tamped) again in several different ways, the use of permanent or removeable shuttering, the option to plan overlapping trades and sequencing all these build elements in a timely manner (workflow management and drying time). These decisions are greatly facilitated by the handbook guide which has been developed in tandem with the 'main output' document. This is a visual tool that illustrates the Decision Matrix and the Build Elements with charts and diagrams facilitating the possibility of minimising the impact of constraints in resolving the optimum design scheme.

## Ongoing Research

The second section is informed by my more recent reflections on 'lessons learned' together with a more in-depth investigation of the Political Philosophical and Economic factors of bio-based construction that I have been researching academically during my time at CVUT. This has given me a reaffirmation that the benefits of this construction method are gradually becoming more widely recognised and will almost certainly result in its wider adoption in the small to medium sized construction sector in the coming years. I believe I have been able to identify a growing body of evidence that the 'fear of the unknown' aspect of hempcrete is progressively giving way as the Post-Occupancy Evaluation of its performance characteristics and the suitability of its technical compliance becomes more widely disseminated.

## The Two Documents

As described above the main output of this thesis is contained in a printed and bound A4 document in portrait format following the normal traditions of an index followed by many numbered sections, a conclusion, appendices and bibliography. In addition to this main thesis document I have also produced a specifiers 'handbook'. This is an A5 booklet in landscape format that is almost exclusively charts and graphs. It is bound in such a way that the options available for consideration by specifiers, as they contemplate the optimum solution for their prospective hempcrete construction, are seen side by side on pull out pages.

This tool facilitates a full understanding of the differences between the options at each stage as they follow the Decision Matrix as directed in the main document. I have not replicated detail drawings published elsewhere but referenced them when helpful to encouraging a new understanding of 'how to select an appropriate construction path' before detailing begins.

It is important that the two documents are seen as complimentary and inter-dependent. They are presented this way to ensure the most comprehensive communication of the importance of carefully studying each element of the wall build-up logic as the design scheme is developed.

## Conclusion

My overarching intention is to prove that building with hempcrete should not be casually dismissed as a 'non-standard' construction method with a myriad of complexities. But rather as a viable, and often advantageous alternative method of constructing buildings with better characteristics of; overall fitness for purpose, reduced environmental impacts, life cycle durability and circularity of materials.

# Contents:

## Section One – The ‘Main Output’

Based largely on my personal experience of working with Hempcrete and other compatible Bio-based materials. Exploring the benefits of understanding the logic of design decisions driven by careful analysis of all constraints.

### 1. Introduction

- 1.1 Why This Guide Exists.
- 1.2 Who This Guide Is For.
- 1.3 What This Guide Covers
- 1.4 How to Use This Guide
- 1.5 What This Guide Is Not
- 1.6 The Bigger Picture

### 2. Matrix Thinking: A New Way to Approach Design Decisions

- 2.1 Why a Design Matrix?
- 2.2 Why Now?
- 2.3 Early Constraints=Better Results.
- 2.4 From Full Walkthrough to Embedded Logic
- 2.5 Outputs That Adapt.
- 2.6 Structure Over Prescription.
- 2.7 A Living System.
- 2.8 Beyond the Matrix.

### 3. Why Constraints Come First.

- 3.1 Planning & Permits – What You are Allowed to Build.
- 3.2 Party Walls – Unlocking Your Options.
- 3.3 Constraint Driven Design – Letting the Site Guide You.

### 4. Phasing Hempcrete Construction

- 4.1 Phasing by Wall Hierarchy
- 4.2 Casting in Sequence – Not Simultaneously
- 4.3 Occupied Buildings and Retrofitting
- 4.4 Tools Setup and Shuttering Types

### 5. Choosing a Construction Method

- 5.1 The Two-Tier Logic: Frame + Hempcrete
- 5.2 Method Comparison: Cast Spray Blocks Panels
- 5.3 Supporting Tools: Decision Matrix & Heat Maps
- 5.4 Method-by-Method Logic

## 6. Moisture Management and Breathable Detailing

- 6.1 Why Breathability Matters
- 6.2 Material Compatibility and Vapour Profiles
- 6.3 Junctions: The Weak Points
- 6.4 Detailing Hybrid Wall Systems
- 6.5 Selecting the Right Insulation Strategy
- 6.6 Final Notes and Decision Flow

## 7. Specification & Technical Integration

- 7.1 Specifying Hempcrete in Tender Packages
- 7.2 Working with Engineers and Frame Designers
- 7.3 Fire and Moisture Compliance
- 7.4 Linking Specification to The Decision Matrix

## Section Two – The ‘Ongoing Research’

Based on examining some ‘lessons learned’ that now inform my wider understanding of this topic. Together with observations concerning; developments in best practice, changes and developments in compliance, and increased awareness in the construction sector. Leading to an analysis of initiatives that might promote growth in the uptake of construction using hempcrete and other bio based materials.

## 8. Coordinated Delivery: Risk Management for Bio-Based Construction

- 8.1 The Coordination Problem
- 8.2 Why Hempcrete Amplifies the Risk
- 8.3 Design and Build as a Remedy
- 8.4 Practical Implications For Hempcrete Projects
- 8.5 Cautions and Caveats
- 8.6 Summary: Towards Joined-Up Bio-Based Buildings

## 9. Non-Standard = High Risk?

- 9.1 The Invisible Barrier
- 9.2 Why Insurers Are Cautious
- 9.3 Fire Testing and Performance Reality
- 9.4 The Mortgage and Lending Knock-On Effect
- 9.5 Strategies for Navigating Insurance Barriers
- 9.6 The Role of Policy and Industry Advocacy
- 9.7 De-Risking the Unknown
- 9.8 Post-Occupancy Evaluation
- 9.9 What Should be Measured
- 9.10 Mainstreaming Hempcrete Projects
- 9.11 Summary: Feedback is a Form of Risk Management

## 10. End-of-Life and Circularity in Hempcrete Construction

- 10.1 From Sustainable to Regenerative Thinking
- 10.2 Hempcrete's Material Lifecycle
- 10.3 Design for Disassembly: Unlocking Circular Potential
- 10.4 Risk of Contamination and Hybrid Systems
- 10.5 Material Reuse - Pathways and Examples
- 10.6 Summary: Designing for the Second Life

## 11. Labour Skills and Training Needs

- 11.1 No Transition Without Trades
- 11.2 What Skills are Needed for Hempcrete?
- 11.3 Training Pathways: Current State and Gaps
- 11.4 Apprenticeships, On-Site Learning, and Design-Build Integration
- 11.5 Upskilling Designers, Engineers, and Site Managers
- 11.6 Summary: No Transition Without Training

## 12. Digital Tools: Bridging Craft and Computation

- 12.1 Bio-Based Meets Digital
- 12.2 BIM Integration: Current Limitations and Potential
- 12.3 Parametric Design and Fabrication Logic
- 12.4 DfMA and Hempcrete: Towards Precast Systems
- 12.5 Digital Risk Management and Sequencing
- 12.6 Summary: From Bespoke to Repeatable

## 13. Precedent Tracking and Regulatory Influence

- 13.1 Data Shapes Policy
- 13.2 Why Hempcrete Needs a Shared Project Database
- 13.3 Precedent as Policy Influence
- 13.4 Summary: Building the Evidence Base

## 14. Conclusion & Recommendations

## 15. Acknowledgements, Bibliography and References

## 16. Appendices

- 16.1 Hygrothermic Simulations
- 16.2 Heat Maps
- 16.3 The Specifiers Handbook
- 16.4 Hempcrete Wall Samples
- 16.5 Built Case Study

# SECTION ONE - The Main Output

## 1 - Introduction

A Practical Guide to Hempcrete Construction for Architects, Builders & Specifiers. The development of a tool to facilitate best option selection when preparing a design scheme based on hempcrete construction methods.

### 1.1 Why This Guide Exists

Hempcrete has long been celebrated for its carbon storage potential, breathability, and health-promoting qualities. Its potential as a carbon-sequestering, breathable insulation and thermal mass material has been well-documented — but navigating how to actually build with it remains unclear for many architects and builders. (Stanwix and Sparrow, 2014).

For most architects and builders, hempcrete exists on the edge of conventional practice: admired from afar, occasionally prototyped, but rarely delivered at scale. The barriers are not just material — they are practical: uncertainty around drying times, confusion over construction methods, limited detailing resources, and difficulty specifying it confidently within tight budgets or planning constraints. (Material Cultures, 2021).

This guide is designed to bridge that gap — turning material promise into buildable, detail-rich solutions for contemporary homes and extensions. It recognises that hempcrete isn't a one-size-fits-all answer, but rather a versatile system that can adapt to a range of contexts — if detailed and delivered with care (Ecomatters and Sustainable Traditional Building Alliance, 2021).

### 1.2 Who This Guide Is For

This guide is written for architects, design-builders, self-builders, and contractors who want to use hempcrete but need help making it work on site. It's also a tool for developers, clients, and engineers to understand the decisions involved and the trade-offs between different construction approaches.

### 1.3 What This Guide Covers

The guide focuses on practical implementation of hempcrete systems, particularly cast-in-situ applications with supporting reference to block, spray and prefabricated panels.

The core tool is a **decision matrix**, developed as a visual logic system to match wall strategies with real-world project constraints. This matrix is presented in the accompanying handbook as a compact, pull-out chart, with illustrated references and compatibility guides.

This main document expands on the matrix's logic through chapters covering:

- Key construction decision points
- Specification and sequencing
- Moisture management and breathability
- Fire, finishes, and material selection

The overall aim is not just to promote hempcrete, but to help professionals adopt a wider **bio-based palette** — combining hemp with cork, clay, straw, and timber to create breathable, low-carbon buildings.

## 1.4 How to Use This Guide

This guide is built around a **decision matrix** — a visual tool that helps match wall strategies to project constraints.

The matrix appears as a compact reference chart in the handbook, showing:

- Which **casting methods** are viable under different site constraints
- Which **framing types** are compatible with different wall build-ups
- How **construction choices** affect drying time, labour, and finish timing

This main document provides the **context and reasoning** behind each decision - through thematic chapters, sequencing charts, and detailed construction analysis.

Use this guide in several ways:

- Read front-to-back for a deep dive into material thinking and workflows
- Jump into specific chapters (e.g. Party Walls, Specification) as questions arise
- Use the matrix and drawing system in the handbook to test design variations in practice

## 1.5 What This Guide Is Not

This is not a catalogue of finished buildings or a restatement of existing academic research; neither is it a theoretical manifesto. Instead, it's a working tool grounded in practice, structured for delivery, and designed to be adaptable and referenceable on-site.

Where high-quality resources already exist — on lifecycle carbon, policy advocacy, or general material science, or policy — this guide references them rather than repeating them (Röck et al., 2020).

## 1.6 The Bigger Picture

This guide aims to be part of the solution — a **translator** between innovation and implementation. One that meets people where they are: on-site, in practice, and under real-world pressures to deliver well.

By focusing on buildability, compatibility, and material logic, this guide hopes to help bio-based construction move from niche to normal — starting with hempcrete, and expanding outward.

## 2. Matrix Thinking: A New Approach to Design Decisions

### 2.1 Why a Decision Matrix?

Designing with hempcrete isn't about one single method or material. It's about combining many interdependent factors — site constraints, finish requirements, construction method, sequencing, material compatibility, thermal targets, and more. A matrix allows these decisions to be visualised not as a linear process but as a **network of dependencies**, where changing one variable reshapes the others.

This matrix approach is not a checklist. It's a tool to **narrow the field** — to help designers, builders, and specifiers identify which strategies are viable before committing to drawings or site logistics.

### 2.2 Why Now?

Bio-based construction is growing — but slowly. One reason is that decisions are still made using conventional logic and standard detailing. But natural materials, and hempcrete in particular, behave differently. Their performance, drying time, labour requirements, and thermal logic demand **a different way of thinking**. The matrix brings that thinking to the front of the design process, not the back.

### 2.3 Early Identification of Constraints = Better Results

Many key decisions are often made too late — like the positioning of a timber frame within a wall buildup or the direction from which the wall can be accessed on site. These factors drastically affect what's buildable, how long it will take, and how the wall performs thermally.

By defining these constraints up front, designers can rule out incompatible strategies early on. This leads to **fewer revisions**, better detailing, and more confidence on site.

### 2.4 From Full Walkthrough to Embedded Logic

The original intent of this thesis was to create a fully traceable decision path — a worked example where every step of a hypothetical project would lead to specific outputs (e.g. Detail 4.2.3 or Wall Type D5). But as the research evolved, it became clear that the **number of viable combinations was too large** to capture in a single flow.

Instead, the project now introduces **matrix logic through embedded tools** within the accompanying handbook. A key example is the fold-out chart, which organises construction choices by **frame position**, **casting direction**, and **shuttering strategy**. Rather than following a walkthrough, the reader can **read the chart visually** to see which combinations are feasible.

## 2.5 Outputs That Adapt

Rather than referencing one specific outcome, the matrix approach now outputs a **range of viable systems**. These are supported by thematic diagrams, comparative detail illustrations, and charts showing:

- Internal and external finish timing
- Labour requirements
- Structural frame options
- Compatibility of insulation and racking
- Drying time and build sequencing

Each output is not a fixed answer, but a **tool for project-specific adaptation**. The logic is what's being delivered — not a prescription.

## 2.6 Structure Over Prescription

Whereas conventional detail libraries offer pre-approved solutions, this matrix-led approach offers a **structure for generating appropriate solutions**. The aim is not to add another rulebook, but to help designers and builders work more creatively and confidently within the limits of bio-based construction.

## 2.7 A Living System

The logic introduced here is designed to grow. Each chapter of the handbook builds on it — connecting wall strategies to frame systems, finish types to casting methods, and so on. While this thesis doesn't provide every possible output, it lays the groundwork for a **scalable, adaptable framework** that can evolve through future projects and shared experience.

## 2.8 Beyond the Matrix.

In this sense, the “decision matrix” is not a finished product. It's a **thinking tool** — one that pushes the user to ask:

- What are my site constraints?
- What build-up is realistic here?
- What finishes are appropriate?
- What will this mean for sequencing, labour, and drying?

The real value lies not in selecting a predefined solution, but in understanding why certain decisions will lead to faster, more buildable, and more sustainable outcomes. Unlike a traditional decision tree, the hempcrete matrix is designed as a **constraint-responsive cross-filtering tool**. It reflects the reality that architects and builders rarely move through decisions in a fixed order. One might begin with access constraints and identify a viable casting method, then backtrack to find compatible frame options.

Another might prioritise labour availability, internal sequencing, or desired finishes. The matrix enables users to **enter at any point** — method, frame, access, or sequencing — and trace which combinations remain viable. This non-linear flexibility allows for real-time comparison between competing strategies, reducing redesign risk and aligning decisions with site realities.

## 3 - Why Constraints Come First

It's Site Realities that Shape Hempcrete Projects. This chapter introduces three types of early constraints that significantly influence the outcome of matrix decisions. Successful hempcrete projects don't start with material choices, they start with constraints! What you're allowed to build, where your boundaries lie, and how much access you have to each wall — these factors shape every design decision that follows. A good hempcrete strategy is one that acknowledges these limits early and uses them to narrow the range of viable options in a structured way.

### 3.1 Planning and Permits – What you are Allowed to Build

In the UK, small-scale projects often begin under **Permitted Development (PD)** rules, which allow certain extensions, roof modifications, or outbuildings without full planning permission. But these permissions come with strict limitations — especially when it comes to **materials and finishes**.

For example:

- **External materials under PD must be 'similar in appearance'** to those of the existing house — often brick, tile, and cement-based renders (Planning Portal, 2024).
- **Rear extensions** are limited in depth and height, meaning thermal mass, insulation thickness, and internal floor levels may be compromised if not considered early.
- **Loft conversions** often permit only rear dormers, while front-facing dormers or gable-end extensions usually trigger full planning approval.

The key is not just what PD allows, but how it limits the ability to use hempcrete visibly or expressively. Where unconventional finishes like cork or lime render are desired, or roof pitch/height changes are needed to suit bio-based construction logic, **applying for full planning permission may be essential** — even for projects that technically fall within PD scope.

Impacts on the matrix:

- Restricts finish options to match existing buildings (MHCLG-2019)
- May eliminate visible cork or exposed hempcrete solutions
- Limits wall thickness in boundary-adjacent conditions
- May necessitate compromise wall strategies (e.g., internal insulation only)

## 3.2 Party Walls – Unlocking or Limiting Your Options

**Party walls** — shared walls between properties — are often overlooked in design stages, but they carry major consequences for how and where you can build. In terraced and semi-detached housing, party wall considerations influence:

- **Access rights and notification requirements** (under the Party Wall etc. Act 1996)
- **Fire resistance requirements**, especially at roof junctions
- **How insulation and airtightness are installed**, particularly if external access is limited or if cavity bridging must be avoided

For example, a double-skin masonry party wall provides excellent fire separation and racking resistance — but can be difficult to insulate thermally at the junction if slabs protrude (BRE, 2020). Meanwhile, timber-framed party walls allow for clean integration with internal hempcrete or bio-based plasters, but may need additional fire detailing at floor and roof lines.

Depending on the project, **party wall strategy can become a load-bearing element** in the broader structural logic. In some designs, the party wall "does all the work," carrying floors and roof loads so that front and rear walls can be more flexible and open.

### Impact on the matrix:

- Determines allowable wall build-up strategies at the property edge
- May dictate fire resistance approach (material and thickness)
- Influences whether floors/roofs can be supported by party walls
- Affects compatibility with certain frame and bracing strategies

## 3.3 Constraint-Driven Design – Letting the Site Guide You

Not all constraints are legal — many are practical. For example:

- **A rear extension that touches the property boundary** may have no external wall access. This means you can't apply shuttering from the outside, and must cast from the inside — requiring internal space and careful planning (Ecomaterials Guide, 2023).
- **A rural detached home**, on the other hand, might have access on all sides. In this case, you may choose to install permanent internal boards and cast from the outside, freeing up interior space for follow-on trades.

These differences determine what types of formwork and casting methods can be used — and whether a given finish is compatible. Internal lime plaster, for example, requires full drying time of the wall; a wood-wool board finish can be applied immediately, but limits future changes.

The **matrix logic** accounts for these constraint patterns by offering four main casting types — each defined by how and where hempcrete is installed. These methods are only viable if site access supports them. By identifying these issues first, we reduce drawing overload and avoid proposing wall types that won't work in a given context.

### Impact on the matrix:

- Filters out incompatible casting methods based on wall access
- Helps sequence internal vs. external works without costly pauses
- Reveals the real effect of finishes on drying time and project flow

### Summary: Start With the Constraints

Constraint Type	Why It Matters	Matrix Effect
Planning/PD	Limits material expression, wall thickness, and roof form	Eliminates non-matching finishes or thick walls
Party Walls	Controls load paths, fire safety, and insulation strategy	Sets limits on wall structure and frame logic
Wall Access	Determines casting method and shuttering approach	Filters viable hempcrete installation methods

Before drawing your wall section, consider your constraints. They don't just limit what's possible — they clarify what's appropriate. The decision matrix is not just a design tool, but a **process of elimination** that helps you reach smart, feasible, buildable solutions.

## 4. Phasing Hempcrete Construction

Hempcrete is often dismissed as slow, but this stems from a misunderstanding of its drying process and its role in construction sequencing. This chapter clarifies how to work with drying times, not against them—showing that with intelligent phasing, interior work can continue uninterrupted

### 4.1 Phasing by Wall Hierarchy

Phasing strategies depend heavily on **which wall type is being built**. Different walls impose different constraints in terms of access, sequencing, and buildability.

Understanding this hierarchy is key:

- **Boundary walls:** Often against other buildings or fences; typically require casting from one side only.
- **Party walls:** Shared with neighbours; usually loadbearing and built early.
- **Return walls:** Structurally crucial for racking resistance; must be sequenced to enable other walls to follow.
- **Front/rear walls:** Often have large openings, affecting shuttering and curing logistics.

Correct sequencing of these walls helps to unlock efficient construction. For example, finishing a party wall early can support floor installation, enabling other trades to continue while hempcrete dries elsewhere.

### 4.2 Casting in Sequence - Not Simultaneously

One of the most common misunderstandings about hempcrete is that it must be completed all at once. In practice, hempcrete is best cast **in logical phases**, allowing drying and site activity to overlap.

- **Roof-first sequencing** offers early weather protection, meaning interior works (first fix, MEP, internal walls) can proceed while external hempcrete dries.
- **Permanent internal shuttering** (e.g. wood wool board) allows casting from the outside, freeing up the internal space for ongoing work.
- **Formwork scheduling** allows limited resources (like reusable shutters) to be moved efficiently across the site.

This approach transforms drying time from a bottleneck into a parallel process. The decision matrix and time-bar diagrams in the handbook help visualise this logic.

### On-Site Training

Where teams are new to hempcrete, even brief on-site demonstrations can dramatically improve outcomes. Understanding compaction, mix moisture, and edge detailing through a trial panel can prevent weeks of rework.

The simplest hempcrete projects succeed not because they are easy — but because they are well rehearsed (Stanwix and Sparrow, 2014) .

### 4.3 Occupied Buildings and Retrofitting

In retrofit scenarios, phasing must respect occupancy. Casting large areas in situ may not be viable—alternatives like **hempcrete blocks** or **precast panels** can reduce disruption and drying time.

- **Internal-only casting** is often necessary due to access limits or planning constraints.
- **Room-by-room sequencing** allows portions of a house to remain in use during works.
- **Dehumidifier-assisted drying** can speed up curing in sensitive retrofit cases, though this adds energy and equipment cost.

Even in complex retrofits, smart phasing allows work to continue while walls dry. The key is to plan casting direction and internal finishing independently.

### 4.4 Tools Setup and Shuttering Types

Strategic phasing only works if site setup supports it.

- **Mixing:** For cast systems, mobile site mixers or pre-batched deliveries determine achievable daily wall area.
- **Formwork:** Removable shutters suit repeat use across walls; permanent shutters (e.g. wood fibre boards) double as finishes.
- **Fixings:** Window reveals, floor edges, and return corners often require temporary bracing or reinforcement during casting.

The six shuttering types in the handbook are explained with diagrams showing how they fit into phased builds. Each has benefits depending on wall type, method, and access.

## Summary

Phasing hempcrete construction is not about eliminating drying time but about working around it. With a roof-first approach, intelligent shuttering, and wall-specific sequencing, drying becomes a manageable variable. The decision matrix and bar charts in the handbook support this process—ensuring that hempcrete can integrate even into time-sensitive projects.

## 5. Choosing a Construction Method

The decision to build with hempcrete is not a single choice—it is a sequence of linked decisions based on site conditions, labour availability, structural needs, and programme constraints. This chapter explains how the four primary hempcrete construction methods—cast in situ, spray-applied, blocks, and panels—can be selected using a matrix approach, supported by framing logic, shuttering strategies, and heat map comparisons.

### 5.1 The Two-Tier Logic: Frame + Hempcrete

Every viable hempcrete wall system begins with the frame. The choice of frame (e.g., single stud, double stud, post-and-beam, or post-and-beam + frame) dictates what casting methods are feasible.

- **Encased frames** (e.g., single stud fully within the wall) are ideal for cast-in-situ or spray.
- **Exposed or post-and-beam frame types** may suit panel or block systems.
- **Double-stud frames** are often required where permanent shuttering or dual finishes are applied.

Once a frame strategy is selected, the casting method can be filtered through project constraints—especially drying time, site access, and labour.

### 5.2 Method Comparison: Cast Spray Blocks Panels

Each hempcrete method brings distinct performance and construction qualities:

Method	Pros	Constraints / Limitations
<b>Cast In Situ</b>	Low-tech, adaptable, excellent infill control	Requires time cure, repeated shuttering
<b>Spray-Applied</b>	Fast, clean, high-volume per day	Overspray risk, requires training and tools
<b>Blocks</b>	Minimal curing time, modularity	Thermal bridges, more waste at cut edges
<b>Panels</b>	Pre-made, fast on-site, good for rainy sites	Heavy logistics, less adaptable on-site

Decision drivers include:

- **Programme:** How soon finishes must start.
- **Access:** Can walls be reached externally?
- **Finish type:** Is cladding preferred over plaster?
- **Drying time:** Does the project need immediate sequencing overlap?
- **Labour:** Will a large, trained team be present, or is a low-skill system preferable?

## 5.3 Supporting Tools: Decision Matrix + Heat Maps

The **decision matrix** introduced in Chapter 3 narrows down viable wall systems by process of elimination. Users input constraints (access, finish, structural exposure) and are left with 2–3 viable options.

To compare these options quickly, the handbook provides a series of **heat maps**:

- **Internal Works Start:** Compares how soon work can begin inside the building.
- **Finishes Start:** Indicates delays until lime plaster or internal finishes can be applied.
- **Labour Intensity:** Rates the manual effort required to maintain consistent casting without gaps.

These heat maps allow rapid visual comparison between shuttering and casting combinations—making the handbook a useful on-site tool for real-time decision-making. More detailed construction bar charts are made available online via QR code.

"While full timelines are available digitally, the handbook simplifies them into comparative heat maps that highlight the drying, access, and sequencing implications of each method."

## 5.4 Method-by-Method Logic

### Cast In Situ:

- Pairs well with internal permanent shutters (wood wool, board) and external access.
- Ideal for small- to mid-sized sites with a single team.
- Works best with temporary formwork that can move quickly across walls.

### Spray:

- Suited to projects with trained applicators.
- Reduced formwork needs, but greater setup cost.
- Often paired with breathable external sheathing or cladding.

### Blocks:

- Best for tight retrofit zones where drying cannot delay sequencing.
- Can work between standard stud frames.
- Strong thermal performance when designed with continuity in mind.

### Panels:

- Effective for off-site construction, but limited adaptability.
- Typically paired with post-and-beam systems.
- May require pre-design of service runs and structural details.

## **Summary**

There is no “correct” hempcrete method—only a method that best fits the constraints of a particular project. The decision matrix and heat maps together create a structure that allows these decisions to be made quickly, collaboratively, and with confidence. When constraints are understood early, hempcrete becomes a flexible tool rather than a limitation.

## 6. Moisture Management and Breathable Detailing

Hempcrete performs best when used within a construction system that respects its breathable character. This chapter explores how to design and detail for moisture-safe, vapour-open assemblies across different construction methods, insulation strategies, and junctions.

### 6.1 Why Breathability Matters

Breathability in buildings does not mean air leakage or draughts. Instead, it refers to the ability of materials to allow **moisture vapour** to migrate safely through the building envelope and evaporate, rather than becoming trapped.

Hempcrete and other bio-based materials are hygroscopic—they **buffer humidity**, helping stabilise indoor comfort and reducing condensation risk. But this capacity only works if the rest of the wall, floor, and roof assemblies also allow vapour diffusion.

#### Key principles of breathable construction:

- Avoid internal vapour barriers.
- Use plasters, renders, or boards that allow moisture to pass.
- Design junctions to maintain the diffusion path.
- Keep the outer layers more vapour-resistant than the inner ones (but still vapour-open).

These principles ensure that moisture generated internally (e.g. cooking, breathing) can move outwards without condensing at cold interfaces. (Goodhew and Griffiths, 2005).

### 6.2 Material Compatibility and Vapour Profiles

Hempcrete alone is not enough to ensure good moisture performance. All adjoining materials must be compatible. Vapour-impermeable layers (e.g. foil-backed plasterboard, vinyl paints, closed-cell foams) can trap moisture inside hempcrete, reducing durability and increasing mould risk.

Layer Type	Compatible Options	Avoid
Internal finish	Lime plaster, clay plaster, wood fibre board	Gypsum + paint, vinyl
Insulation (additional)	Cork, wood fibre, hemp batts, sheep's wool	PIR, PUR, EPS
External cladding	Timber, lime render, ventilated facades	Plastic rainscreens

**Thermal upgrades** in retrofit projects often fail when non-breathable insulation is added to otherwise breathable walls. Vapour becomes trapped at interfaces, leading to decay. Even breathable materials must be detailed carefully to ensure continuity.

## Final Thought

Moisture buffering is not a niche bonus — it is a core feature of how hempcrete supports occupant wellbeing and building durability. A correctly detailed hempcrete wall doesn't just meet insulation values — it contributes actively to indoor humidity stability, material protection, and passive energy efficiency.

## 6.3 Junctions: The Weak Points

Most moisture issues arise not in the middle of a wall, but at junctions—where floors, roofs, or windows interrupt continuity. Each junction should be designed to:

- Maintain the vapour diffusion path.
- Avoid cold spots and thermal bridges.
- Use breathable materials consistently.

Junction	Risk Factor	Solution
<b>Floor-wall base</b>	Cold edge = condensation risk	Aerogel strip / cork / stepped build-up
<b>Roof-wall eaves</b>	Cold bridging, plasterboard contact	Lime parge / breathable airtightness layer
<b>Window reveals</b>	Trapped vapour at impermeable frame	Splayed reveals with wood fibre / cork
<b>Internal partitions</b>	Trap vapour against external wall	Ventilated cavity or breathable separation

### Note

Performance failure rarely occurs in the middle of a hempcrete wall. It happens at the edges — where modern construction practices rely on plastic foams, tapes, or membranes that disrupt the wall's natural moisture management system. Every successful bio-based building depends on coherent breathable detailing.

## 6.4 Detailing Hybrid Wall Systems

In many builds, hempcrete is combined with other systems—timber frame, brick, internal clay blockwork, or cavity wall retrofits. Each introduces new interfaces.

### Strategies for safe hybrid construction:

- Always test the full build-up using WUFI or equivalent tools.
- Avoid sandwiching hempcrete between two low-permeability layers.
- Use ventilated cavities if external brickwork is retained.
- Interrupt horizontal floor slabs with a diffusion break where possible.

**Key detail:** External walls that retain non-breathable finishes (e.g. stucco, painted brick) should not be insulated internally with thick hempcrete unless a capillary break and ventilation strategy is introduced.

## 6.5 Selecting the Right Insulation Strategy

Insulation choices influence drying behaviour. Some strategies work with the hempcrete; others compromise it. The goal is always to **minimise interstitial condensation**.

### Example decision logic:

- Cast from both sides → internal finish = lime / clay plaster → no added insulation.
- Cast from inside only → add external cork or wood fibre to boost thermal performance.
- Internal retrofit with retained external brick → use hemp blocks or light clay only if ventilation is added.

## 6.6 Final Notes and Decision Flow

Moisture-safe detailing depends on understanding both **material properties** and **assembly interactions**. Good practice avoids risk—not by banning insulation or demanding perfection, but by asking smart questions during design:

With the right approach, hempcrete becomes part of a healthy, durable, and resilient envelope system—especially when detailed with breathability in mind.

## 7. Specification & Technical Integration

Hempcrete is not a standalone material; it's part of a wall system that must be carefully specified and coordinated to deliver thermal, fire, and structural performance. This chapter outlines how to integrate hempcrete correctly into architectural packages, focusing on specification logic, structural compatibility, and regulatory compliance.

### 7.1 Specifying Hempcrete in Tender Packages

Good specification ensures hempcrete is used appropriately within the project context. This includes stating the **casting method**, **shutter type**, **thickness**, and **interface logic** with adjacent elements.

#### Example Tender Language:

*"Apply cast hempcrete insulation (Method 3P: cast from inside with permanent shutter) to 300mm thickness. External face to use Steico Protect Dry 60mm as permanent shutter. Internal face left exposed for later finish. Frame depth set to 360mm. Interface with steel beam to be isolated using cork expansion tape. All work in accordance with [Matrix Handbook Reference]."*

[Graphic: Sample Spec Sheet + Matrix Snapshot]

A full list of recommended specification fields is below:

Field	Example Entry
Wall Casting Method	Method 2S (Cast from Outside, Removable Shutter)
Shutter Type	Permanent Wood Fibre Board (P)
Hempcrete Thickness	300mm
Finish	Internal Lime Plaster
Interface Instructions	Break at floor slab, cork wedge at steel junction
Relevant Detail Reference	See Detail D3.2 – Gable End Junction

[Reference: Detail Book, Section D – Method Variants]

### 7.2 Working with Engineers and Frame Designers

Since hempcrete is non-structural, coordination with the **structural frame** is critical. Hempcrete only performs well when the frame is fully self-supporting and allows for consistent shuttering and infill logic.

#### Key Coordination Points:

- **Stud Spacing:** For cast hempcrete, 400mm centres are optimal. Larger spacing (e.g. 600mm) is acceptable with deeper members.

- **Bracing:** Racking resistance must come from timber bracing (e.g. Agepan, diagonal members, or plywood). Hempcrete contributes no shear strength.
- **Sequencing:** The frame must be installable and self-supporting before casting begins.
- **Movement & Shrinkage:** Hempcrete shrinks ~0.5% as it cures. Fixings must allow for this movement.

It's essential to confirm these constraints early in the structural brief. Many failures occur not from material problems, but from frames designed without awareness of hempcrete's behaviour.

## 7.3 Fire and Moisture Compliance

Hempcrete achieves **Class B-s1,d0** fire performance with lime render or clay plaster finishes. It is inherently vapour-open and can contribute to hygrothermal buffering—but it must be part of a continuous breathable build-up.

### Fire Performance Summary

Wall Build-Up	Fire Resistance Rating (EN)	Notes
Cast Hempcrete + Lime Plaster (both sides)	REI 60–90	Fire-stable up to 100mm load
Double Brick + Hempcrete Infill	REI 120+	Suitable for party walls
Hempcrete + Wood Wool Board + Clay Render	REI 30–60	Non-loadbearing interior partition

### Moisture Detailing

Use WUFI-tested assemblies and breathable tapes at junctions. Avoid hybrid strategies that mix vapour-open with impermeable membranes unless cavity venting is continuous and controlled.

[Ref: WUFI Appendix Case #6 and #7]

### Checklist for Compliance:

- No OSB or PU foam at junctions
- Avoid steel fixings embedded directly in hempcrete
- Ensure drying time before airtightness testing (typically 8 weeks for 300mm wall)

## 7.4 Linking Specification to The Matrix

This chapter feeds directly into the matrix system. Every wall build-up in the handbook is paired with:

- A casting method (1–4)
- A shutter type (P, S, B)
- A structural logic (e.g. braced stud, post and beam)
- Fire and moisture compliance indicators

This allows specifiers to narrow down appropriate combinations without needing to memorise performance data. Instead, the decision matrix visually filters what works based on access, drying time, labour, and finish.

The matrix allows the specification and frame design to evolve **in parallel**, rather than one chasing the other. This reduces redesign, aligns procurement, and ensures that hempcrete succeeds in practice—not just on paper.

## Section Two – The ‘Ongoing Research’

Section 2 examines some ‘lessons learned’ that now inform my wider understanding of this topic together with observations concerning; future developments in best practice, changes and developments in compliance, increased awareness in the construction sector. and some available data indicating a progressive growth in the uptake of construction using hempcrete and other bio based materials.

### 8. Coordinated Delivery: Risk Mitigation for Bio-Based Construction

In conventional construction, a degree of disconnect between design and execution is often tolerated. Architects produce drawings, builders interpret them, and minor adjustments are made on site. But in bio-based construction — especially with materials like hempcrete — this gap can prove catastrophic. A misplaced membrane, an over-tamped wall, or an incorrect drying allowance is not just a site hiccup; it’s a fundamental system failure

#### 8.1 The Coordination Problem

Hempcrete, by its nature, demands precise sequencing, breathable layer logic, and careful handling — all of which rely on tight coordination between those who draw and those who build. This chapter explores Early Contractor Involvement (ECI) strategies and the Design and Build (D&B) model as not simply a procurement choice, but an essential framework for success when working with natural construction systems.

#### 8.2 Why Hempcrete Amplifies the Risk

Hempcrete is often celebrated for its forgiving thermal performance and its ability to regulate indoor humidity — but these benefits only emerge when the material is correctly detailed and applied. Unlike synthetic insulation systems, hempcrete is part of a larger environmental balance: it must breathe, dry, and remain protected from excess moisture (Evans et al., 2020).

Errors that might be harmless in conventional builds — like trapping condensation behind an airtight layer or rushing plaster application — can lead to mould growth, decay, or structural degradation in hempcrete walls (Walker & Pavia, 2014).

What’s more, the material’s relatively slow curing time and non-standard thicknesses make construction sequencing critical. In this context, the traditional handoff from architect to builder becomes a liability. Without early-stage alignment on construction logic, the project is at risk before the first formwork is set.

## 8.3 Design & Build as a Remedy

In the context of hempcrete construction, the design and build model offers more than just contractual efficiency — it offers risk mitigation. With the same team responsible for both design intent and site execution, there's a much smaller margin for misinterpretation. Details are no longer passed down a chain of subcontractors with varying levels of understanding, but instead developed in conversation with those who will implement them. This results in practical, buildable solutions tailored to real material behaviour.

Crucially, design and build teams can adapt sequencing and construction methods in response to project-specific constraints — such as access, drying time, and curing conditions — without compromising the integrity of the bio-based system. A cast-in-situ hempcrete wall, for instance, may require bespoke shuttering, staged pours, or adjusted weather protection, all of which benefit from direct input between designer and builder during the planning phase (Ramage et al., 2017).

Furthermore, materials like hempcrete benefit from hands-on knowledge. A contractor with on-site experience of tamping, drying cycles, and natural plastering techniques can flag issues long before they reach the construction stage. This feedback loop — where design is informed by craft — helps eliminate common failures such as inconsistent wall densities, thermal bridging at junctions, or over-engineered frames compensating for poor detailing.

## 8.4 Practical Implications for Hempcrete Projects

For hempcrete projects to succeed, coordination must begin before the first drawing is finalised. Design decisions like wall thickness, window placement, or insulation strategy all have construction consequences — especially when using formwork, large volumes of wet material, or breathable finishes. A design and build model enables this interdependency to be addressed holistically, not retrofitted at tender stage.

One of the most effective strategies is early contractor involvement (ECI). When the contractor, hempcrete installer, and frame supplier are consulted during early design phases, the result is a smarter build-up — one that considers shuttering logistics, scaffold requirements, drying time allowances, and sequencing overlaps. For example, external casting may be viable on a rural site with access on all sides, but on a narrow urban infill plot, internal shuttering with rear infill may be the only workable method. These are decisions best made with builder input, not assumptions.

Another key implication is role clarity. Hempcrete buildings require specialist trades — but also clear leadership. In a design and build setup, the boundaries between architect, builder, and specialist can be formally integrated, allowing for continuous feedback while still protecting the design vision. Misunderstandings — like confusing limewash with breathable render or installing membranes where vapour openness is required — are far less likely when the detail authors and detail implementers are in direct communication (BRE, 2016).

This model also supports iterative prototyping. Test panels, on-site mockups, or small-scale pilot builds can be coordinated and reviewed by the same team that will carry out the full project. These not only validate technical performance, but help educate less experienced trades, giving them a tactile understanding of drying behaviour, formwork pressure, and finish application.

## 8.5 Cautions and Caveats

While the design and build model offers a strong framework for bio-based construction, it is not a universal fix. Poorly executed design and build can be just as problematic as fragmented delivery — sometimes worse, if neither side possesses deep knowledge of bio-based systems. A joined-up contract is no substitute for competence.

One major risk is oversimplification. In an effort to streamline decision-making or reduce cost, some design and build teams may remove essential design detailing or substitute materials that appear equivalent on paper but behave differently in practice. Vapour-open construction, in particular, leaves little margin for error. Substituting a breathable insulation layer for one with a foil-faced vapour barrier, for example, can compromise the entire wall assembly (Rode et al., 2017).

There is also the risk of design dilution, where the architectural vision is compromised by cost-led decisions. Hempcrete buildings, more than most, rely on thoughtful proportions and well-resolved junctions to deliver both performance and aesthetic presence. A design and build approach must therefore be rooted in shared values — not just efficiency. The best outcomes are achieved when architects retain strong authorship of the spatial and environmental agenda, while builders bring practical methods and refinements to support that vision.

Finally, it's worth noting that contractual design and build and collaborative design and build are not the same thing. The former may simply mean the contractor owns the drawings post-tender; the latter requires early-stage collaboration, open communication, and mutual respect for each party's expertise. In the context of natural materials, only the latter is viable (Hill & Norton, 2022).

## 8.6 Summary: Towards Joined-Up Bio-Based Building

The success of a hempcrete project is rarely determined by product choice alone. It is shaped by sequencing, by detail, and by the willingness of the design and construction teams to operate as one. In bio-based building, where performance depends on breathability, curing, and careful junctions, this joined-up approach is not a luxury — it's a necessity.

Design and build offers a practical route toward this alignment, provided it is applied with care, competence, and shared intent. It enables projects to avoid the common pitfalls of miscommunication, last-minute substitutions, and detail clashes on site. It fosters a culture where the designer understands construction constraints, and the builder understands material logic.

This chapter has shown that with hempcrete — a material that blurs the line between structure, insulation, and finish — integrated delivery isn't just a better way to work; it's the only way to build with confidence. When architecture and construction are treated as one continuous process, the result is not only a more resilient building, but a more resilient system of building — fit for a bio-based future.

Design-and-build delivery helps prevent detailing errors on site — but other barriers remain beyond the architect or builder's control. Insurance providers, mortgage lenders, and warranty assessors continue to view hempcrete and other bio-based materials as non-standard. The next chapter explores the roots of this perception, and how to navigate the insurance and finance ecosystem to reduce risk and support adoption.

## 9. Non-Standard = High Risk?

Despite its excellent fire resistance, low environmental impact, and increasing use in eco-conscious construction, hempcrete is still classified by many relevant institutions as a **'non-standard' material**. This label carries real-world consequences. This chapter explores the challenges facing hempcrete and other bio-based systems, and outlines strategies to help designers, builders, and clients navigate the current limitations of the construction finance and insurance markets.

### 9.1 The Invisible Barrier

For all the technical attention paid to thermal performance, moisture safety, and material detailing, one of the most significant barriers to the adoption of hempcrete remains largely invisible in the early design stages: insurance. In turn, these insurance uncertainties can delay mortgage approvals, deter developers, and undermine confidence in what is otherwise a high-performing, low-risk material system.

### 9.2 Why Insurers Are Cautious

From an insurer's perspective, risk is not defined solely by how a material performs in the lab — it is shaped by precedent, familiarity, and claims history. Hempcrete, like many bio-based materials, lacks the long-term datasets and repair case studies that underpin conventional insurance models. As a result, it is typically grouped under the umbrella of 'non-standard construction,' alongside cob, straw bale, timber frame, and other systems outside the brick-and-block norm.

The concerns are varied. Combustibility is often cited, despite the fact that hempcrete is non-combustible once cured and performs well in fire resistance tests (BRE, 2016). Insurers may also raise questions about durability, pest resistance, or repairability following water ingress — even if the actual failure rates are low. These concerns are not always based on known issues, but on lack of familiarity: if a building system is not well understood, it is seen as unpredictable and therefore higher risk.

Another common challenge is that hempcrete, when used structurally or as insulation, may not conform to British Standard categories for wall or roof construction. This can trigger hesitation from underwriters when no matching reference exists in their systems. Where materials are not pre-approved by warranty providers (such as NHBC or LABC), developers may be asked to provide third-party accreditation, private fire test results, or engineer's reports — adding time, cost, and uncertainty to the process.

In effect, insurers are not just evaluating risk — they are evaluating confidence. Until bio-based materials gain mainstream recognition in warranty schemes and insurers' internal databases, this lack of confidence will continue to be treated as a premium risk factor, regardless of the actual building performance.

## 9.3 Fire Testing and Performance Reality

One of the most persistent myths surrounding hempcrete and other bio-based materials is that they are inherently flammable. This assumption is understandable at a glance — after all, hemp is an organic material — but it is fundamentally incorrect when it comes to cured hempcrete.

Hempcrete is a composite of hemp shiv (the woody core of the plant) and a lime-based binder. Once set, the material forms a dense, mineralised matrix with exceptional fire resistance. Independent testing has shown that hempcrete can withstand fire exposure for well over 60 minutes without structural failure or flame penetration, with charring confined to surface layers (Evans et al., 2020). In many cases, performance exceeds the minimum UK requirements for fire resistance in both domestic and low-rise commercial applications.

Tested to standards such as BS EN 1365-1, hempcrete wall panels have achieved REI 60–120 fire ratings, depending on thickness and framing (Walker & Pavia, 2014). Unlike synthetic insulation or timber panelling, hempcrete does not emit toxic fumes when exposed to heat, and its lime content acts as a natural fire retardant, slowing ignition and flame spread.

Yet despite this robust data, hempcrete is still often treated as a fire risk in the absence of a long claims history or standardised test documentation pre-approved by warranty providers. In practice, this means that insurers may still apply premiums or require bespoke testing, even when the material outperforms many common alternatives.

The gap, therefore, is not in performance — it is in industry familiarity. Until more projects publish fire data and demonstrate compliance through third-party certification or warranty-backed systems, hempcrete will continue to face misplaced assumptions about combustibility.

## 9.4 The Mortgage and Lending Knock-On Effect

The challenges posed by insurance classification don't stop with the building's policy — they also influence how easily buyers or developers can secure finance. Most lenders rely on standard insurance categories to assess construction risk, particularly for new-build homes, self-builds, or major retrofits. If a material like hempcrete is flagged as 'non-standard' by the insurer, the lender may hesitate to approve the mortgage, demand additional warranties, or require higher deposits.

This can create a cascade of delays and extra costs for both individual clients and small developers. Even when the material is performing well on site, if it falls outside recognised systems — such as those backed by NHBC, LABC Warranty, or BOPAS — it may be viewed as experimental. Lenders typically prefer buildings that conform to standard construction norms: brick or block walls, mineral insulation, and fire-tested floor systems.

For first-time buyers, this can result in restricted access to mainstream lenders or products with unfavourable terms. For developers, it may reduce resale value or complicate pre-sales on schemes where mortgage buyers need reassurance about insurability and durability.

There are efforts underway to expand what counts as insurable and mortgageable. For example, the Build Offsite Property Assurance Scheme (BOPAS) was developed to reassure lenders about the longevity and resilience of non-traditional systems. But most bio-based materials, including hempcrete, are not yet formally covered by BOPAS — either due to a lack of proprietary systemisation or because they fall outside modular construction models.

Until these schemes broaden their scope or new certification routes are developed for natural materials, lending hesitancy will remain a systemic bottleneck in the widespread adoption of hempcrete in mainstream housing.

## 9.5 Strategies for Navigating Insurance Barriers

While hempcrete currently sits outside the comfort zone of many mainstream insurers and lenders, these barriers are not insurmountable. A growing number of self-builders, architects, and developers have successfully insured and financed hempcrete buildings — but success often depends on proactive engagement and the ability to provide clear documentation early in the process.

One of the most effective strategies is to work with specialist insurance brokers who are familiar with eco-builds and low-impact construction. These brokers understand the material performance and can match clients with underwriters who are open to non-standard projects. In many cases, a tailored policy is still possible — but only if approached with the right technical evidence and framing.

Providing robust supporting documentation is essential. This may include:

- Third-party fire test results (e.g. BS EN 1365-1 rated wall assemblies) [ref image above](#)
- Evidence of successful use in other insured UK buildings
- Engineer's reports verifying structural systems
- Confirmation of vapour control strategy and breathability
- Site-specific design details, especially where lime renders, shuttering systems, or timber framing are used

Where formal certification schemes (such as Agrément certificates or LABC approvals) are unavailable, manufacturer's data and project case studies become even more valuable. In some cases, developers have been able to secure warranty cover by bundling multiple elements under a recognised structural system (e.g., timber frame with lime-based insulation) and clearly documenting how the overall wall assembly meets performance criteria.

Another strategy is to engage warranty providers during the design stage, rather than after construction begins. Some warranty firms are more flexible when brought in early and allowed to review design choices. This aligns well with the broader thesis argument that early integration — not just of trades, but of institutions — improves project outcomes.

While these steps require time and care, they also present an opportunity: projects that succeed in navigating these insurance hurdles create precedents. The more this is done, the easier it becomes for future bio-based projects to follow — and the more pressure is applied to insurers to modernise their standards.

## 9.6 The Role of Policy and Industry Advocacy

While individual projects can navigate insurance barriers through careful documentation and expert support, the long-term solution lies in systemic change. Insurers, lenders, and warranty providers don't operate in a vacuum — they respond to standards, regulations, and industry norms. For hempcrete and other bio-based materials to become truly mainstream, policy and advocacy bodies must lead the way in redefining what is considered 'standard.'

One of the most effective routes is through certification and pre-approval frameworks. If bio-based materials can be formally recognised within schemes like NHBC Standards, LABC Registered Details, or BOPAS, they are far more likely to be accepted without additional paperwork or premiums. This would require test data, detailing protocols, and case histories to be consolidated and submitted at scale — ideally led by industry consortia rather than individual firms.

There is also an important role for publicly funded demonstration projects and pilot schemes. Programs such as the UK's Home of 2030, Future Homes Standard, and emerging Bio-Based Homes initiatives aim to normalise low-carbon construction and help insurers see bio-based systems as low risk, rather than unfamiliar. When these projects include independent performance monitoring and third-party assessments, they become powerful tools for risk reassessment.

In parallel, professional bodies such as RIBA, LETI, ASBP, and AECB can influence insurance acceptance by publishing guidance, collecting performance data, and advocating for standards reform. By aligning architects, engineers, and material manufacturers under a shared umbrella, these organisations can help demystify hempcrete and support insurers in developing more nuanced risk models.

Many experienced industry leaders would now argue that government could play a catalytic role by updating building regulations, planning guidance, or procurement frameworks to formally recognise low-carbon, bio-based solutions as compliant — not experimental. This would reduce uncertainty and signal to the financial sector that these materials are not fringe innovations, but part of the national climate response.

Without this multi-level push — from projects, professionals, and policymakers — the ‘non-standard’ label will persist, regardless of performance. But with it, the path is open to creating a new standard: one that reflects the realities of a low-carbon, bio-based construction future.

## 9.7 De-Risking the Unknown

Insurance is often treated as a peripheral issue — something to be arranged after design is complete. But for hempcrete and other bio-based materials, it remains one of the most powerful gatekeepers to widespread adoption. Performance is not the problem; perception is. In the absence of long-term claims data and standardised warranties, insurers continue to treat hempcrete as an unknown — and in the insurance industry, the unknown is synonymous with risk.

This chapter has shown that many of the industry’s reservations stem from habit, not evidence. Fire safety, durability, and performance in bio-based buildings are demonstrably strong — yet without familiarity, these strengths are often overlooked. Until natural materials like hempcrete are integrated into standard risk models and certification pathways, they will remain caught in a feedback loop: too unfamiliar to insure easily, and too difficult to insure to become familiar.

Breaking that loop requires action on multiple fronts. Designers must prepare to document and defend their material choices. Builders and manufacturers must gather case studies and test data. Industry bodies must push for new standards. And policymakers must treat bio-based insurance access as part of the transition to low-carbon construction — not as a niche concern.

In short, de-risking hempcrete is not just a technical task, but a cultural one. Only by making the unfamiliar familiar — through advocacy, education, and repetition — can we build a future in which natural materials are seen not as exceptions, but as the new standard.

Despite strong technical performance, hempcrete buildings are often treated with suspicion by insurers due to a lack of long-term data. One of the most powerful tools to counter this perception is Post-Occupancy Evaluation (POE). By tracking real-world outcomes, designers and developers can build the evidence base needed to shift how hempcrete is understood and accepted by institutions.

## 9.8 Post-Occupancy Evaluation

Post-Occupancy Evaluation (POE) is the process of assessing how a building performs once it is occupied. While often overlooked in conventional practice, POE is especially critical for bio-based buildings, where long-term performance depends on both material behaviour and user interaction. In the case of hempcrete, POE helps move the conversation from theory to evidence — providing data on how hempcrete buildings behave over time, across seasons, and in response to real occupancy patterns.

This is particularly important for three reasons. First, many of the claimed benefits of hempcrete — thermal inertia, moisture buffering, and indoor air quality — are difficult to measure during construction or handover. Second, POE helps validate detailing decisions made during the design-build process: Is there condensation at known thermal bridges? Is heating demand in line with predicted U-values? Third, POE contributes to the larger credibility of bio-based construction by building a growing dataset of monitored buildings, which can support insurance, mortgage, and regulatory conversations (Leaman & Bordass, 2001; AECB, 2022).

Without POE, the risk is that natural buildings remain anecdotal, with performance either over- or under-estimated by third parties. With it, architects and clients can demonstrate success — and learn from shortfalls — in a measurable and repeatable way.

## 9.9 What Should Be Measured

A well-designed POE balances quantitative monitoring with qualitative feedback. For hempcrete and other vapour-open assemblies, key metrics include:

- Indoor Relative Humidity (RH) — to assess moisture buffering and whether rooms drift into mould-prone ranges (>75% RH)
- Internal temperature fluctuations — especially in shoulder seasons, where thermal inertia can reduce energy spikes
- Energy consumption for heating and hot water — to compare against design-stage SAP or PHPP models
- Surface and interstitial moisture — in areas like window reveals or floor-wall junctions
- Airtightness and ventilation performance — particularly relevant if mechanical ventilation or hybrid strategies are used
- Occupant perception — collected through surveys, interviews, or diary-based methods to understand comfort, usability, and lived experience

Tools can range from data loggers (e.g. HOBO, Tinytag) and wireless sensor arrays, to simple manual readings and occupant-led observations. Even low-budget POE can yield valuable insights if deployed consistently and interpreted with care (Stevenson & Leaman, 2010).

Architects and builders do not need to reinvent the wheel to run POEs. A number of recognised frameworks offer templates and guidance for small or self-build scale:

- Soft Landings Framework (BSRIA/UCL): A step-by-step POE guide for the post-handover phase, designed to align expectations between users and designers (BSRIA, 2014)
- RIBA Post Occupancy Toolkit: Simplified methodology for architects, including surveys and monitoring advice
- AECB Building Performance Evaluation: Focused on low-energy buildings, includes humidity, CO<sub>2</sub>, and thermal comfort tracking (AECB, 2022)

- Passivhaus Trust POE Protocol: Focused on monitored airtight buildings, but adaptable for hempcrete where similar comfort goals are pursued

These tools allow bio-based POE to be lightweight, low-cost, and repeatable, making it accessible for smaller practices and early-stage developers.

## 9.10 Mainstreaming Hempcrete Projects

A small hempcrete housing scheme or self-build project might apply POE in the following ways:

- Install RH and temperature sensors in multiple zones (bedrooms, living rooms, north/south walls) to track seasonal buffering
- Compare heating bills against PHPP predictions or SAP estimates to verify thermal performance
- Interview occupants at 3, 6, and 12 months to understand how they perceive thermal comfort, window operation, and any issues with breathability (e.g. condensation on glazing, summer overheating)
- Check moisture content in key junctions using spot meters or embedded probes — especially around sills, reveals, and bridging-prone details
- Track plaster performance, cracking, or signs of moisture ingress over time as part of a visual audit

If published — even as a short report or blog post — this kind of data helps build industry confidence. For firms pursuing repeatable hempcrete housing, POE can also inform refinements such as adjusting insulation depth, modifying junction detailing, or reconfiguring ventilation strategies. Notably, case studies from France and the UK suggest that many hempcrete buildings perform more thermally stably than their calculated U-values would suggest, due to combined effects of thermal mass, breathability, and solar gains (Ramage et al., 2017). POE is the only way to document these effects in context.

For hempcrete to move from niche to norm, data is key. POE provides the kind of robust, user-centred evidence that insurers, lenders, and regulators increasingly demand. In fact, some insurers are beginning to recognise POE data as a legitimate form of risk reduction — especially when it demonstrates fire safety, humidity control, or durability across multiple builds. On the design side, POE encourages a feedback culture where mistakes are seen as learning opportunities rather than liabilities. In bio-based building, where performance depends on craft, detail, and material integrity, this learning loop is invaluable. It helps avoid repetition of failures (e.g. inadequate shading, trapped moisture, improper detailing of breathable junctions), and builds practitioner confidence over time.

## 9.11 Feedback is a Form of Risk Management

Hempcrete buildings already perform well — but in a sceptical industry, evidence is more persuasive than claims. Post-Occupancy Evaluation gives natural buildings a

voice, allowing them to demonstrate what they do best: regulate humidity, reduce heating demand, and support healthy, resilient living environments. By closing the loop between design, construction, and occupation, POE helps refine future buildings, increase confidence among stakeholders, and support the shift toward a more accountable, bio-based construction culture. For a material that depends on trust, feedback may be the most powerful tool we have.

# 10 End-of-Life Circularity in Hempcrete Construction

While POE allows us to monitor buildings in use, sustainability must also extend beyond occupancy. The end-of-life phase — often ignored in conventional construction — is where bio-based materials like hempcrete show powerful advantages. This chapter explores how to design with disassembly, reuse, and circularity in mind, closing the material loop.

## 10.1 From Sustainable to Regenerative Thinking

Hempcrete is widely promoted as a sustainable material — but true sustainability extends beyond the point of handover. As circular economy principles gain traction in construction, designers and builders must consider what happens at the end of a building's life, not just how it performs during occupation. This includes questions about reuse, disassembly, biodegradability, and the long-term management of material cycles.

Unlike many conventional systems that rely on synthetic adhesives, foam insulation, or mixed-material composites, hempcrete offers significant advantages at end of life. Its biodegradable core, non-toxic binder, and monolithic nature allow for recovery and reuse strategies that align with circular construction goals — provided the building is designed with this in mind (Anderson et al., 2018; Dodd et al., 2021).

## 10.2 Hempcrete's Material Lifecycle

Hempcrete consists of hemp shiv (the woody by-product of the hemp plant) mixed with a lime-based binder. Once set, the material carbonates slowly over its lifetime, locking in CO<sub>2</sub> and forming a stable, mineralised body. At end of life, hempcrete walls can be:

- Crushed and returned to the soil as a pH-neutral amendment (if uncontaminated)
- Recycled as aggregate in new hempcrete or lime-based screeds
- Landfilled without risk of leaching or off-gassing (though this is discouraged)
- Stored for future reuse in low-grade applications (e.g. insulation infill or rammed earth bases)

These outcomes contrast sharply with synthetic insulation (e.g. PIR/PUR), which is energy-intensive to produce, typically non-recyclable, and often landfilled or incinerated at end of life (WRAP, 2019).

However, end-of-life performance is not just about the material itself. It depends on how the material is assembled — and whether it is paired with compatible components. A breathable wall becomes less recoverable if clad in cement render or bonded to petrochemical membranes.

## 10.3 Design for Disassembly (DfD): Unlocking Circular Potential

To support circularity, hempcrete buildings must be designed for disassembly. This means reducing material fusion, avoiding irreversible joints, and enabling selective deconstruction without contamination. Key principles include:

- Dry joints wherever possible — using screws, laths, or mechanically fixed cladding
- Avoidance of synthetic foams or sealants, which can trap moisture or render components non-recyclable
- Modular formwork or block systems that can be taken apart and reassembled
- Lime plasters and renders, which are both breathable and removable (if not overpainted with plastic-based finishes)

For example, timber frames filled with sprayed or cast hempcrete can be recovered more easily if the external cladding is bolted or clipped, and if internal finishes are lime-washed or clay-plastered rather than sealed with acrylic paints.

Precast hempcrete blocks and panels (e.g. IsoHemp, UK Hempcrete panel systems) may offer even better circular potential, particularly if their installation avoids wet adhesives and instead uses lime mortar or dry stacking techniques.

## 10.4 Risk of Contamination and Hybrid Systems

In practice, one of the biggest obstacles to circularity is material contamination — when breathable, reusable materials are bonded to synthetic layers or paints that prevent recovery. Common risks in hempcrete construction include:

- Acrylic or silicone renders applied to hempcrete façades
- Expanding foam used around windows or penetrations
- Bitumen or plastic-based damp proof courses (DPCs)
- Glues and tapes that are not lime-compatible or bio-based

While sometimes necessary for warranty or regulation compliance, these materials can reduce end-of-life value and complicate disassembly. Where possible, bio-based alternatives — such as cellulose-based sealants, paper tapes, or hemp-fibre DPCs — should be prioritised (Sassi, 2008).

## 10.5 Material Reuse - Pathways and Examples

Though formal recycling infrastructure for hempcrete is limited, on-site reuse is already possible in many cases. Crushed hempcrete can be used for:

- Non-structural internal insulation in refurbishments
- Floor infill or sub-base layers in new builds

- Garden walls or landscape features (as low-carbon aggregate)
- Acoustic buffering in stud wall assemblies

There is growing interest in re-deployable hempcrete panels that can be lifted and relocated — though this depends on careful design and robust fixing systems. Experimental projects in Europe have explored “plug-in” natural wall modules that could be refitted into future builds, extending material life and reducing waste (BioBuild, 2015).

## 10.6 Summary: Designing for the Second Life

Hempcrete offers a compelling pathway toward circularity — but only if we design with disassembly in mind. When treated as a recoverable resource rather than inert fill, hempcrete’s low-toxicity, lime-bound structure becomes a clear advantage. End-of-life circularity is not just about reducing landfill. It’s about shifting the mindset from linear building lifespans to continuous material cycles, where every component can have a second or third life. For hempcrete to support this future, architects and builders must avoid contaminating layers, use reversible fixings, and document material choices clearly for future disassembly teams.

In this way, hempcrete buildings can become more than low-carbon — they can become material banks, ready to regenerate and re-form in the next generation of construction.

Circular design principles only succeed when they are matched by skilled hands. Designing for disassembly or vapour-open performance is not enough if builders, trades, and site managers lack the knowledge to deliver it. The following chapter examines the critical role of training and labour pathways in ensuring that bio-based buildings meet their potential.

# 11. Labour Skills and Training Needs

Bio-based construction is often praised for its low environmental impact, healthy indoor climate, and renewable resource base — but without a skilled workforce, these materials can't reach the market. In the case of hempcrete, labour is not just a delivery mechanism: it's a critical enabler of performance. The quality of the final result depends heavily on mixing, placing, tamping, and drying control, as well as careful detailing at junctions, reveals, and finishes.

## 11.1 No Transition Without Trades

Despite increasing demand, hempcrete and other natural materials remain largely absent from mainstream trade training. Most UK construction workers — from site operatives to site managers — are trained in standard blockwork, plasterboard, and mineral insulation systems. As a result, introducing hempcrete often means retraining existing workers, or building specialist teams from scratch (Anderson & Woodward, 2017). Without investment in bio-based training pathways, even the best-designed buildings risk underperformance or delay.

## 11.2 What Skills Are Needed for Hempcrete?

Hempcrete sits at the intersection of multiple trades, blending aspects of:

- Timber framing (formwork layout, wall spacing, shuttering)
- Plastering (internal lime plasters, natural finishes)
- Insulation and air-tightness installation (layer control, continuity)
- On-site mixing and batching (correct ratios, moisture levels, flowability)
- Team coordination for cast-in-situ workflows (two-person minimum recommended)
- Moisture management (weather protection, drying curves, surface prep)

The required skill set is broader than for most conventional materials. A team member must understand not just how to install the material, but why certain conditions matter (e.g. vapour openness, thermal continuity, surface preparation for adhesion). This implies a need for values-driven training, not just task-based.

## 11.3 Training Pathways: Current State and Gaps

A handful of UK and European organisations currently offer formal hempcrete training:

- UK Hempcrete Ltd – runs multi-day hands-on workshops for designers and builders
- Hemp-LimeConstruct – offers CPD and on-site guidance
- Terre et Humanisme / La Maison en Paille (France) – offer natural building apprenticeships

- Ecological Building Systems (Ireland) – delivers broader training on airtightness, vapour control, and breathable construction

However, there is no nationally accredited hempcrete qualification within the UK’s Construction Skills Certification Scheme (CSCS) or mainstream NVQ frameworks. As a result, most tradespeople are unaware of hempcrete unless introduced through a specialist build.

This creates a feedback loop: few trained teams = fewer hempcrete builds = limited familiarity = higher perceived risk. To break this loop, hempcrete must be embedded into national training bodies such as CITB, City & Guilds, or NOCN. Doing so would allow new workers to gain hempcrete experience as part of their normal learning, rather than having to specialise later.

## 11.4 Apprenticeships, On-Site Learning, and Design–Build Integration

One of the most effective training strategies is hands-on apprenticeship within design–build teams. Unlike off-site modules, this approach allows trainees to see how hempcrete interacts with timber frames, membranes, window details, and roof junctions in real time.

Design–build firms that specialise in hempcrete (e.g. Green & Castle, Natural Building UK) are increasingly taking on apprentices or interns, enabling younger tradespeople to develop skills through repetition, site adaptation, and seasonal variation. Training in this way builds not just skill, but also confidence, allowing teams to improvise intelligently on site — a crucial ability when working with climate-sensitive, moisture-variable materials like hempcrete.

To scale this, public procurement bodies and local authorities could require low-carbon skills exposure as part of framework agreements or project-based contracts — especially for social housing and retrofits.

## 11.5 Upskilling Designers, Engineers, and Site Managers

It’s not just site labour that needs support. Hempcrete success also depends on informed professionals who understand its limits, tolerances, and sequencing requirements:

- Architects need to know what thicknesses, curing times, and junction details are practical on site
- Engineers must understand the composite behaviour of hempcrete with timber or steel frames
- Site managers must plan for drying time, shuttering logistics, and curing protection
- Quantity surveyors must allow for manual batching, transport, and variability in labour rates

Training modules for professional audiences can take the form of CPD, toolbox talks, or web-based simulations, ideally delivered in partnership with universities, trade federations, or manufacturer-supported networks.

## 11.6 Summary: No Transition without Training

Hempcrete is a low-tech material — but high-quality results require high-context knowledge. Without an investment in labour skills and training pathways, the bio-based construction transition will remain fragile, reliant on a few specialist teams and unable to scale effectively. Mainstreaming hempcrete requires embedding it in national training curricula, offering apprenticeship opportunities, and supporting on-site learning environments where values, not just techniques, are passed on. The labour force must be empowered not only to install hempcrete, but to understand and advocate for its broader ecological and cultural value.

As construction decarbonises, skills development will not be a support activity — it will be the main driver of systemic change. Scaling hempcrete construction will depend not only on training people, but on improving tools. Digital workflows — from BIM to DfMA — offer ways to reduce errors, plan more effectively, and make craft-based materials repeatable at larger scales.

## 12. Digital Tools: Bridging Craft and Computation

Bio-based construction is often perceived as analogue — hand-mixed, low-tech, and artisan. Hempcrete, in particular, is known for its tactile nature: tamped by hand, formed in simple shuttering, cured in place. But as the demand for natural materials grows, there is increasing interest in how digital tools — including BIM, parametric design, and Design for Manufacture and Assembly (DfMA) — can support wider adoption of hempcrete while respecting its unique material logic.

### 12.1 Bio-Based Meets Digital

Rather than replacing craft, digital tools can amplify craft knowledge, improve design coordination, and reduce waste. For hempcrete, which depends on exact detailing, careful sequencing, and tight material integration, the benefits are clear: fewer errors, clearer communication, and smarter, faster workflows (Eastman et al., 2018).

### 12.2 BIM Integration: Current Limitations and Potential

Building Information Modelling (BIM) has become the standard for design coordination in many public and private projects — yet BIM libraries for hempcrete are still in their infancy. Many common objects (e.g. Revit families) do not yet include:

- Hempcrete-specific wall assemblies (with correct thermal and moisture behaviour)
- Vapour-open component data (e.g. Steico boards, lime renders)
- Custom formwork strategies or cast-in-place variants
- Time-based logic for curing, protection, and weather vulnerability

As a result, designers often resort to generic “infill wall” categories or fudge hempcrete into rigid insulation templates, leading to miscommunication with engineers and contractors.

To bridge this gap, practices can create custom BIM object libraries with embedded performance values — such as hygrothermal properties, fire resistance (e.g. REI ratings), and environmental data (CO<sub>2</sub>e). Tools like One Click LCA or Ecometrica can be linked to BIM workflows to enable live carbon footprinting, helping designers choose between, for example, cast-in-situ vs panelised hempcrete (Azhar, 2011).

### 12.3 Parametric Design and Fabrication Logic

Hempcrete’s formwork-based application lends itself well to parametric design, where geometry can respond to real-time rules or constraints. In particular, parametric tools (e.g. Grasshopper, Dynamo) can assist with:

- Generating optimal shuttering layouts for varied wall thicknesses
- Adapting panel geometry to site or climate constraints (e.g. solar orientation)

- Pre-sizing ventilation openings based on wall depth and thermal lag
- Mapping thermal bridging risk at complex junctions

Parametric logic is especially valuable in retrofit scenarios, where wall geometries are often irregular. For instance, adjusting insulation depth around joist ends or sills can be automated across hundreds of junctions — reducing coordination errors and improving vapour continuity.

## 12.4 DfMA and Hempcrete: Towards Precast Systems

While cast-in-place remains the most common approach, hempcrete is increasingly being used in panelised or modular formats, particularly in:

- Off-site fabricated hempcrete wall panels (e.g. IsoHemp, UK Hempcrete panels)
- Hybrid CLT–hempcrete assemblies for rapid envelope construction
- Systems with removable formwork for precision-cast façades

DfMA (Design for Manufacture and Assembly) enables these systems to be rationalised early in the design phase, ensuring transportation, on-site handling, and fixings are considered from the outset. Using digital tools, designers can simulate:

- Panel dimensions optimised for lifting gear and truck beds
- Junction detailing that maintains airtightness and breathability
- Dry jointing systems that allow reversible installation (supporting circularity)

These systems make hempcrete more viable for urban infill, multi-unit housing, and other contexts where speed, weather protection, or logistics are critical.

## 12.5 Digital Risk Management and Sequencing

Because hempcrete is sensitive to moisture, temperature, and curing time, digital construction planning tools (e.g. 4D BIM, Gantt sequencing overlays) can help manage:

- Weather risks during casting or panel installation
- Timing for shutter removal and drying
- Integration of other trades without disrupting hempcrete curing (e.g. first fix electrics)
- Site-wide coordination of scaffolding, render curing, and protection layers

Embedding this logic into BIM or scheduling tools helps prevent errors such as premature render application, improper wall covering, or sequencing conflicts.

## 12.6 Summary: From Bespoke to Repeatable

Hempcrete construction will always require human understanding and material sensitivity — but that doesn't mean it must remain low-tech.

By leveraging BIM, parametric tools, and DfMA, practitioners can scale hempcrete beyond custom homes and into repeatable, efficient systems that maintain performance and design integrity.

Digital tools do not replace the values of bio-based building — they support their execution at scale. In doing so, they help align the natural material future with the construction industry's evolving standards, enabling hempcrete to thrive not just as a niche material, but as a mainstream, digitally compatible system.

Digital tools help us design and build smarter — but they also help us collect and share results. Every hempcrete building completed is an opportunity to shape future regulation, if its performance is tracked and published. The final chapter examines how precedent tracking can influence standards, insurance, and mainstream acceptance through cumulative demonstration.

## 13. Precedent Tracking and Regulatory Influence

This chapter explores how systematic precedent tracking can help shift industry perception, support policy reform, and accelerate adoption of hempcrete and other bio-based materials. As the construction sector evolves toward evidence-based standards, the ability to measure, record, and share built outcomes is no longer optional — it is strategic.

### 13.1 Data Shapes Policy

Hempcrete has a strong theoretical and material case — but for most insurers, warranty providers, and regulators, theory is not enough. In practice, industry standards are shaped not by potential, but by precedent: buildings that have been delivered, tested, monitored, and recorded. Without a shared pool of precedent data, hempcrete remains vulnerable to risk-averse responses — even when performance is sound.

In the UK and across Europe, construction standards evolve incrementally. Regulators, insurers, and lenders do not often lead change — they respond to patterns of proven success. A material or method becomes “standard” when:

- It is used repeatedly across diverse contexts
- Its failures are rare, well-documented, and manageable
- Performance benchmarks are consistent and easy to verify
- Case data feeds into formal certification (e.g. Agrément, BBA, LABC)
- It is linked to warranty-backed systems (e.g. NHBC, BOPAS)

For hempcrete, this means that every built project is a potential catalyst. But unless performance is documented, the opportunity is lost.

### 13.2 Why Hempcrete Needs a Shared Project Database

Most hempcrete buildings are bespoke and dispersed — built by small practices or self-builders, with little central documentation. This limits their ability to influence systemic standards.

A national or pan-European hempcrete precedent database could capture:

- Location, build type, wall and roof assemblies
- Construction method (cast-in-place, block, panel, spray)
- Key performance metrics (U-values, airtightness, fire ratings)
- Insurance/warranty success or failure
- Moisture or thermal monitoring results (POE)
- Lessons learned or key detailing strategies

This data would support not only specifiers and designers, but also insurers, lenders, and government agencies trying to assess the viability of bio-based systems at scale (Dodd et al., 2021).

The precedent database should be open-access, peer-reviewed, and curated — not a marketing repository. It could be hosted or supported by:

- ASBP (Alliance for Sustainable Building Products)
- AECB (Association for Environment Conscious Building)
- LETI or RIBA Bio-Based Special Interest Groups
- Academic or EU research bodies (e.g. COST Action, Interreg projects)

Ideally, it would build on existing platforms like Home Quality Mark, Level(s), or the Sustainable Traditional Buildings Alliance (STBA) performance database. Standardised reporting formats — based on PHPP, SAP, or Level(s) templates — would allow consistent benchmarking across regions.

A basic version could even be crowd-sourced: a shared Google Sheet or web form where hempcrete builders log basic project info and outcomes.

### 13.3 Precedent as Policy Influence

Once critical mass is reached, precedent tracking doesn't just help designers — it can help change the rules. When 100+ monitored hempcrete buildings show consistent fire safety, humidity control, and energy performance, there is a stronger case for:

- Reclassification from “non-standard” to “approved system” in insurance underwriting
- Inclusion in SAP modelling databases or approved construction details
- Streamlining planning approvals for natural builds
- Accelerating Agrément certification or LABC Registered Detail pathways

Over time, this allows hempcrete to become a default option, not a speculative risk.

### 13.4 Summary: Building the Evidence Base

Precedent is more than anecdote it is verifiable evidence— it is infrastructure. By treating each hempcrete building as a datapoint, the industry can accumulate confidence, reduce regulatory friction, and push for systemic reform.

Whether self-build, retrofit, or housing development, each project has a role to play in reshaping the regulatory landscape. With coordinated effort and shared learning, hempcrete can shift from marginal curiosity to codified, trusted standard — not just through theory, but through buildings that speak for themselves.

## 14. Conclusion and Recommendations

From the beginning of this Research Thesis, I stated:

“My overarching intention has been to prove that building with hempcrete should not be casually dismissed as a ‘non-standard’ construction method with a myriad of complexities. But rather as a viable, and often advantageous alternative method of constructing buildings with better characteristics of; overall fitness for purpose, reduced environmental impacts, life cycle durability and circularity of materials”.

In endeavouring to make my case I have recognised the **current situation** is that in the UK construction industry adoption is still slow but there are signs of its progressive acceleration. The key concerns in this respect are, not unusually, also the key areas of greatest potential growth.

- Many Architects & Specifiers are not fully conversant with the technical aspects of hempcrete nor sufficiently knowledgeable or confident to recommend it to their clients.
- Many clients are concerned that hempcrete construction is a ‘non-standard’ building method and not prepared or willing to risk its use on their projects.

My Thesis addresses these concerns head on. My experience of working with other architects in this sector is that they have some residual ‘fear of the unknown’ but are open minded when presented with verifiable evidence of its suitability for many projects and increasingly convinced once they appreciate its benefits and start to understand how best it can be executed on site. The Clients side of the reluctance is likely to remain challenging until such time as the categorisation changes from ‘non-standard’ to ‘fully recognised’. That is undoubtedly a harder shift for me to influence directly. I am however optimistic that change is underway and that UK adoption, which is notoriously reticent by nature of anything ‘new or unknown’, is moving in the right direction. My section on the importance of more verified POE is hugely relevant to this re-categorisation. Awareness that hempcrete is being used more extensively in the EU (particularly France, Belgium and Holland) is also encouraging. I have not referenced climate change as a factor in this growth problem but .assumed it to be a ‘given’ in the thinking of most professionals involved in any aspect of the construction industry. Greater awareness of the benefits of the reduced environmental impacts of hempcrete can only be supportive of my proposition.

My construction handbook could be enhanced by the addition of a QR code that would collate data from users as to which build strategies they eventually choose. This data would facilitate the user in being given further directions as to contacts where more detailed design and product information, directly relevant to the execution of their chosen build strategy, could be delivered. By way of a further enhancement to this current project, to ensure its wider adoption by the profession, another next step must surely be the development of a digital library where architects will be able to access 1:1 detail drawings and photographic examples of completed constructions together with list of material suppliers, contractor contacts and case studies. My thinking is that the resultant data base could then be of assistance to users tasked with gathering and

reporting on their projects POE analysis, thus supporting the argument for reclassification from the stigma of being ‘non-standard’. Were this to be initially set up by a project sponsor it could thereafter be self-supporting using an open source framework and continually developed by the user base independently.

My feeling now is that my focus is to continue to work more specifically on the Architects by demonstrating, both by ‘show and tell’ on sites and by the future dissemination of the ideas expressed here (The logic of the Decision Matrix), safe in the knowledge that most architects of my own generation are easily converted to this new thinking once it has been fully and clearly explained. Surely, any increase in the supportive attitude in our profession will filter through to their own clients.

My personal interest in this subject has been greatly reinforced by undertaking this Research Thesis and I look forward to increasing my wider understanding of its growth potential as I continue to investigate the relationship between the farmers growing the crop and the construction industry manufacturers turning it into building products. There are already some big success stories in that sector as growing hemp for commercial use is proving to be a more profitable activity than many standard agricultural product strategies. This would of course be even more attractive to farmers if they were allowed to grow ‘industrial hemp’ without any restrictions as currently imposed by the UK Government under the badly outdated ‘dangerous drugs act’. Given that the farming community are reluctant to grow any sort of crop without there being an off-take agreement in place with a reputable buyer there should be an opportunity here for a major construction materials manufacturer to become the ‘missing link’ between the growers and the builders. Once this link is proven the transition to ‘fully recognised’ would inevitably be unstoppable. It is well known that this sort of vertical integration in big corporations is already happening in many sectors including construction materials so the proposition is increasingly credible.

In closing, I believe that the problems of increased awareness and industry uptake of hempcrete is eminently solvable and I hope to find some involvement in its resolution as I continue with my career in Architecture and The Built Environment.

## 15. Acknowledgements, Bibliography & References

With special thanks for personal interviews and mentoring with:-

Jan Jakub Tesar Ph.D and Ales Marek Ph.D - Tutors & Staff at CVUT  
Will Stanwick - The Hempcrete Book (2014) Stanwick & Sparrow – Green Books, UIT  
Summer Islam - Material Cultures: Material Reform (2024) – mackbooks.co.uk  
Bob Bloore – Practicing Hempcrete Design & Build Contractor

With thanks for ongoing collaboration with:-

Ecomatters and Sustainable Traditional Building Alliance (2021)  
On-Site Constraints and Bio-Based Material Installation: Ecomaterials Guide (2023)  
Extensive Research into Lime Renders – Historic England Buildings

With thanks to the many others referenced in this document:-

Party Walls and Fire Separation in Low-Rise Housing Watford: BRE (2020)  
Spray Applied Hempcrete - UK Hempcrete(2022)  
Thinking in Systems -Donella Meadows – Chelsea Green Publishing (2008)  
Materials Guide MHCLG(2019)  
Retrofit Projects Ecomerchant (2021)  
Boundary Walls – Smith and Tilley (2022)  
Spray systems with Strategic Dry Zones – Adams and Carson (2021)  
Acoustic and Fire Separation – UK Building Regulations – HM Gov (2019a+b)  
Junction Complications and Potential Cold Bridges – Green Structures Journal (2021)  
Moisture Conflicts – WUFI simulations – Evans (2010)  
Vapour Movements – Goodhew and Griffiths(2005)  
Condensation and Microbial Growth – Larsen and Marlow (2013)  
Vapour Gradient Balance - Gonzalez and Garcia Navarro (2006)  
Hygric Mass Fluctuations – Allinson and Hall (2010)  
Spikes in Humidity – Collet and Pretot (2014)  
Dust Mite Activity – Mansouri and El Hanandeh (2021)  
Compatible Adjacent Materials – May and Rye (2012)  
Mixed Material Interfaces -IBP Fraunhofer (2023)  
Structural Degradation in Hempcrete Walls – Walker & Pavia (2014)  
Collaborative Design and Build – Hill and Norton (2022)  
POE Monitored Buildings – Leaman & Bordass (2021)  
Cellulose-Based Sealants – Sassi (2008)  
Retraining Workers- Anderson & Woodward (2017)  
Carbon Footprinting – Azhar (2011)  
Viability of Bio-based Systems – Dodd et al (2021)  
Vapour Diffusion – Walker et al (2014)  
Moisture Regulation Capacity – Rode et al (2007)  
Design & Build Planning Phase – Ramage et al (2017)  
Sequencing and Workflows – Eastman et al (2018)  
Permitted Development Rights: Planning Portal (2024) [www.planningportal.co.uk](http://www.planningportal.co.uk)  
Party Wall etc. Act 1996 (UK): Gov.uk (2023)  
Warranty Providers – NHBC, LABC and BOPAS  
Professional Bodies – RIBA, ASPB, ECOS and AECB

## 16. Appendices

The appendices give further detail to several topics covered in the Thesis document that may assist the reader in gaining further insight into some more complex information.

### 16.1 Hygrothermal Simulations

This appendix presents a series of hygrothermal simulations carried out using WUFI 7.1 to assess the moisture behaviour and thermal performance of common hempcrete-based wall build-ups. The simulations were conducted using a London climate file (London\_UK\_IBP\_HRY) over a 5-year period (2026–2031), under standard interior and exterior conditions.

#### Simulation Method

Each case was tested using dynamic, transient-state analysis to observe how heat and moisture move through the wall over time. Variables such as moisture content, water vapour resistance, insulation strategy, and material porosity were taken into account.

#### Material Codes

Each wall build-up is referenced using a simplified three-letter material code in the format:

Interior – Core – Exterior

#### Examples:

- LHL → Lime plaster / Hempcrete / Lime render
- SCH → Clay Strocks / Hempcrete / Cork
- XKH → Hempcrete / Air gap + membrane / Timber cladding

These codes are consistent throughout the thesis and allow direct comparison between WUFI results, construction methods, and detailing options.

#### Reading the Simulations

Each case includes:

- A short summary of the construction type and materials
- Key values: U-value, Initial & Final Moisture, Peak Water Content
- 2 key graphs:
  - Fig 9.X.1 – Total Water Content over time
  - Fig 9.X.2 – Relative Humidity (RH) profile

#### Interpretation

The most important indicators for performance are:

- Drying trend vs. moisture accumulation
- Peak RH in vapour-retentive layers
- Condensation or mould risk (if any)
- Suitability for the intended construction scenario

## Quick Reference Table

Code	Build-Up Description	U-Value (W/m <sup>2</sup> K)	Moisture Trend	Verdict
LHL	Lime-Hemp-Lime	0.22	Stable drying	Safe, basic breathable wall
LHB	Lime-Hemp-Brick	0.18	Slight rise	Acceptable with care
LHC	Lime-Hemp-Cork	0.14	Strong drying	Ideal for insulation upgrades
LHK	Lime-Hemp-Cladding	0.20	Gradual drying	Suitable with ventilated façade
SCH	Strocks-Hemp-Cork	0.13	Strong drying	Excellent hybrid system
SKH	Strocks-Hemp-Cladding	0.18	Moderate drying	Safe, with timber RH fluctuation
SRH	Strocks-Hemp-Lime	0.19	Slight drying	Safe for rendered hybrids
XBH	Hemp-Brick	0.18	Moisture rise	Use only with rainscreen
XCH	Hemp-Cork	0.14	Strong drying	Excellent for external insulation
XKH	Hemp-Membrane-Cladding	0.20	Moderate drying	Lightweight, safe build-up
XRH	Hemp-Lime	0.22	Slight drying	Minimalist, breathable wall

Note: All U-values and results are based on dry-state simulation outputs. See each case page for full details.

## Hygrothermal Simulation Cases

The full data on each of the above build-ups is available from WUFI.

We have chosen the two highlighted above as generally relevant to the hempcrete construction industry. We use these to review Drying Times and Moisture Trends when contemplating a Wall Build-Up Strategy.

## Code LHL

Build-up: Internal lime plaster (20mm) + Hempcrete (300mm, cast-in-situ) + External lime render (20mm)

Construction type: Cast hempcrete / vapour-open both sides

Climate file: London\_UK\_IBP\_HRY

Orientation: N/A (assumed average)

Total R-value: 4.34 m<sup>2</sup>K/W

U-value: 0.22 W/m<sup>2</sup>K

Simulation Period: Jan 2026 – Jan 2031

Initial Moisture Content: 12.9 kg/m<sup>2</sup>

Final Moisture Content: 11.6 kg/m<sup>2</sup>

Peak Water Content (kg/m<sup>3</sup>):

- Lime Plaster: 241


- Hempcrete: 39.1

- No condensation or mould risk detected


Conclusion: Moisture levels remain stable across 5 years with no accumulation.

Safe for use as an internal-only hempcrete wall with plaster finish.

(See Fig. 9.1.1 for water content over time; Fig. 9.1.2 for RH profile.)

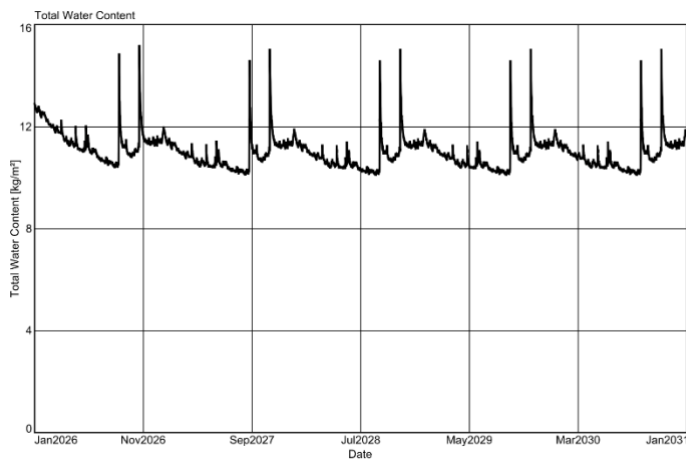

Total Water Content (2026–2031)

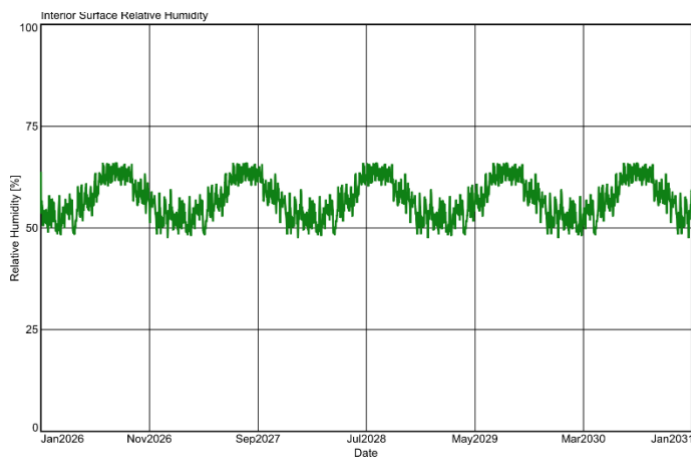

## Code LHB

Build-up: Internal lime plaster (20mm) + Hempcrete (300mm, cast-in-situ) + External reclaimed brick (200mm)

Construction type: Cast hempcrete / vapour-open both sides

Climate file: London\_UK\_IBP\_HRY

Orientation: N/A (assumed average)

Total R-value: 5.43 m<sup>2</sup>K/W

U-value: 0.18 W/m<sup>2</sup>K

Simulation Period: Jan 2026 – Jan 2031

Initial Moisture Content: 14.9 kg/m<sup>2</sup>

Final Moisture Content: 17.1 kg/m<sup>2</sup>

Peak Water Content (kg/m<sup>3</sup>):


- Lime Plaster: 30

- Hempcrete: 39.1


- Brick: 48.5

Conclusion: Moisture levels rise slightly across 5 years but remain within acceptable bounds. No condensation or mould risk detected. Suitable for use as a breathable wall with reclaimed brick exterior.

(See Fig. 9.2.1 for water content over time; Fig. 9.2.2 for RH profile.)

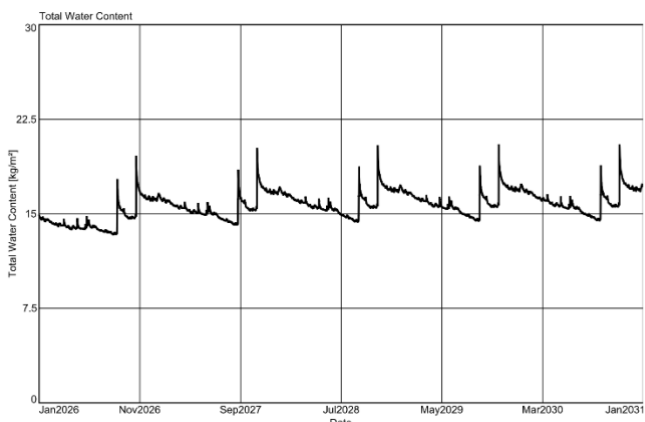


Total Water Content

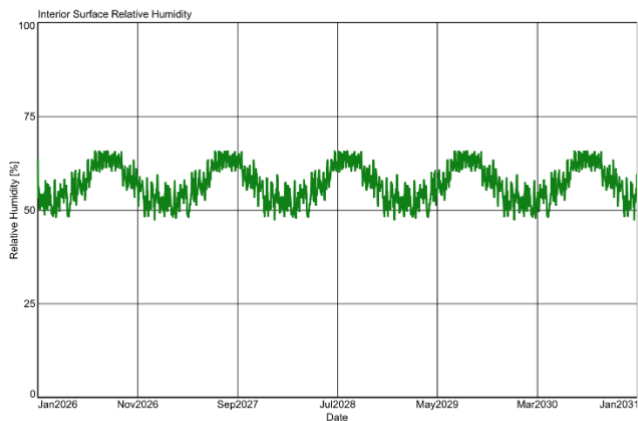

RH profile

## 16.2. Heat Maps

Underlying drying time estimates are derived from WUFI simulations and site precedent. Rather than reproduce each drying curve, this heat map condenses the outcome into a direct finish-readiness comparison across build-up types. Detailed drying charts are included for selected wall types below.

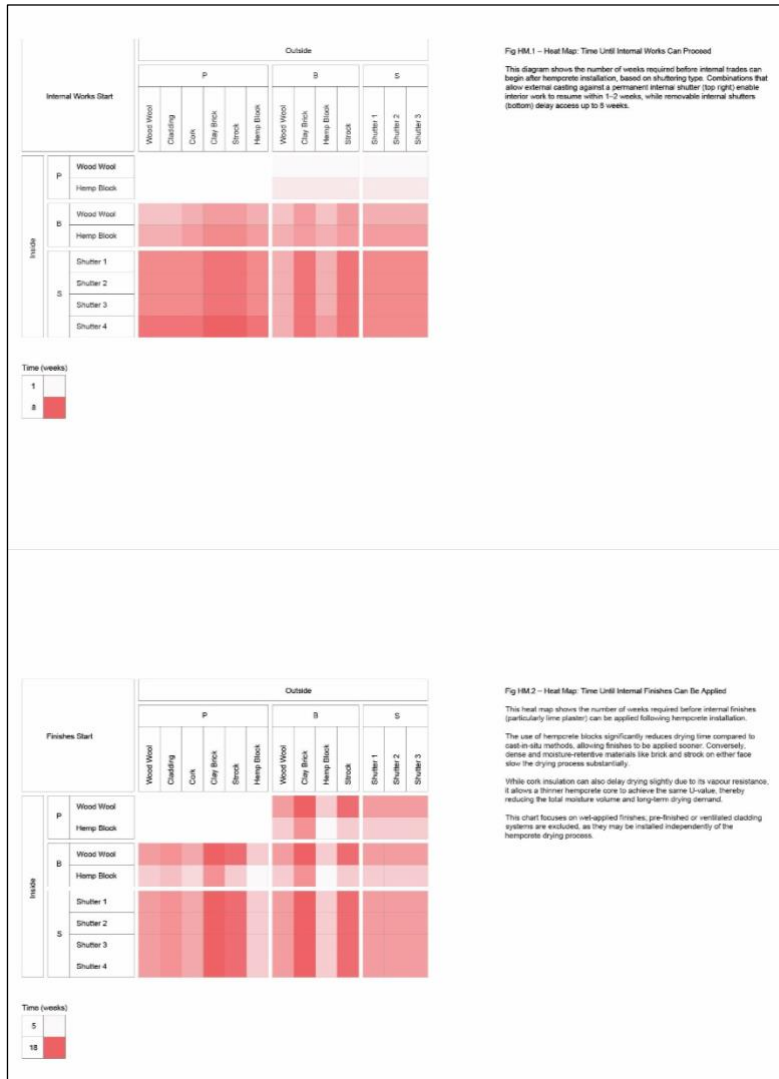

### Time Until Internal Works Can Proceed


This diagram shows the number of weeks required before internal trades can begin after hempcrete installation, based on shuttering type. Combinations that allow external casting against a permanent internal shutter (top left) enable interior work to resume within 1–2 weeks, while removable internal shutters (bottom right) delay access up to 8 weeks.

### Time Until Internal Finishes Can Be Applied

This heat map shows the number of weeks required before internal finishes (particularly lime plaster) can be applied following hempcrete installation.

The use of **hempcrete blocks** significantly reduces drying time compared to cast-in-situ methods, allowing finishes to be applied sooner. Conversely, dense and moisture-retentive materials like **brick and strock** on either face slow the drying process substantially.

While **cork insulation** can also delay drying slightly due to its vapour resistance, it allows a thinner hempcrete core to achieve the same U-value, thereby reducing the total moisture volume and long-term drying demand. This chart focuses on wet-applied finishes; pre-finished or ventilated cladding systems are excluded, as they may be installed independently of the hempcrete drying process.

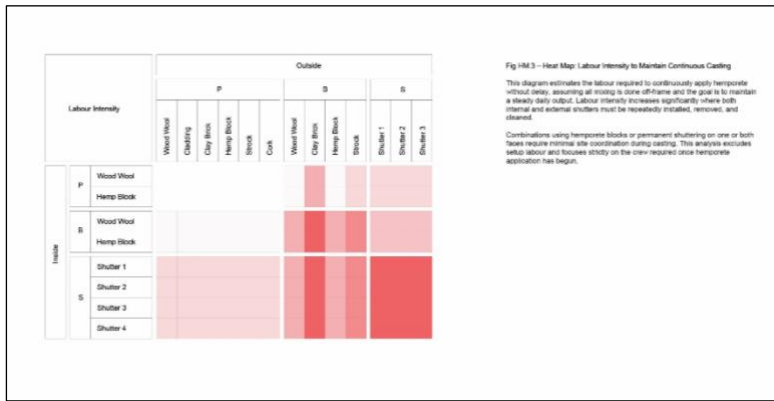

**Labour Intensity to Maintain Continuous Hempcrete Application**

This diagram estimates the relative labour required to maintain consistent hempcrete application across different shuttering combinations. Systems using **removable shutters on both sides** require significant coordination and a dedicated shuttering team to ensure casting continuity.

In contrast, combinations using **hempcrete blocks** or **permanent shutters** on one or both sides allow continuous casting with minimal support labour. The labour score reflects the need for constant shutter repositioning, on-site curing time buffers, and workflow interruptions.


The above three heat maps model the real-world impact of shuttering choices on construction flow, finish timing, and labour intensity. They do not assess theoretical material performance, but rather simulate practical, on-site constraints that shape how and when hempcrete can be applied and finished. These maps are derived from construction experience, typical drying profiles, and sequencing benchmarks gathered from live projects.”

Other heat maps for later could include:

- **Drying time** compatibility
- **Labour demand**
- **Access requirements**
- **CO<sub>2</sub>e impact**
- **Buildability**
- **Weight**
- **Structural depth**
- **Time overlap potential**

## 16.3 The Specifiers Handbook

The Handbook is described in some detail in the main Thesis Document. It is to be presented in a 1:1 printed and bound manner at my presentation on 10<sup>th</sup> June. The format is A5 Landscape with several fold out sections. This is difficult to illustrate here so a sample image PDF of a content page has been included by way of verification only.

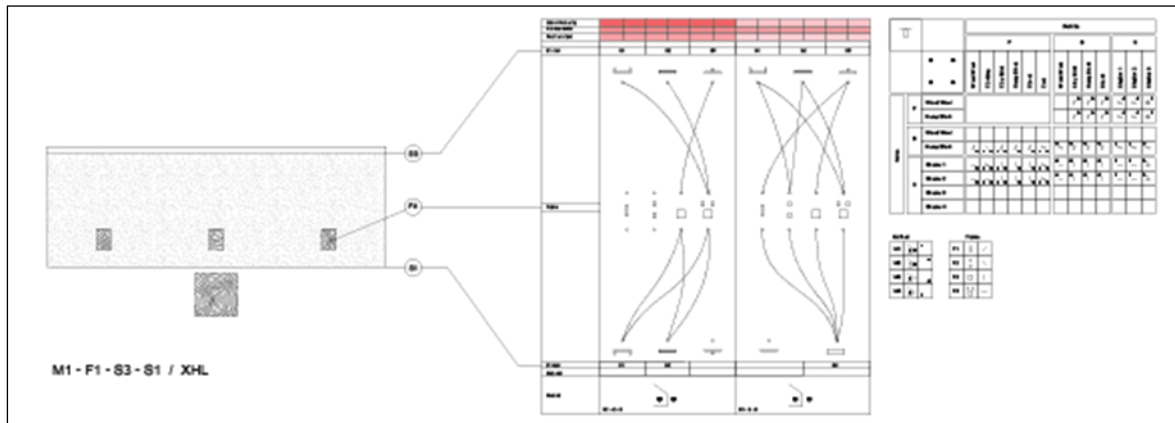

The above sample – Code M1-F1-S3-S1-/-XHL - illustrates the start of the Decision Matrix which runs across 4 pages when folded out. It allows the user to identify a ‘frame type’ and then review how that frame would be compatible with different wall build components.

In this case the Code indicates:-

M1:Method - Casting from both sides

F1:Frame - Single Stud

S3: Shutter Type - Exterior

S1:Shutter Type - Interior

XHL: Material Chart (see WUFI Chart)

(Indicates: Unfinished Hempcrete / Hempcrete / Lime Plaster)

## 16.4. Hempcrete Wall Samples

These 1:1 sample wall mock-ups will be an element of my presentation scheduled for 10th June. They are included here in photographs by way of verification only. I shall also be presenting a display of bio-mass building products as described in various sections of the main Thesis Document. These demonstrate different Frame Builds and Wall Strategies and will be available to be handled and examined in person.



## 16.5 Framed Case Study of a Built Project

This will also be an element of my presentation on 10<sup>th</sup> June